



ELSEVIER

Nuclear Instruments and Methods in Physics Research A 465 (2001) 440–446

**NUCLEAR  
INSTRUMENTS  
& METHODS  
IN PHYSICS  
RESEARCH**  
Section A

www.elsevier.nl/locate/nima

# Quasiparticle diffusion over several mm in cryogenic detectors

M. Loidl<sup>\*</sup>, S. Cooper<sup>1</sup>, O. Meier, F. Pröbst, G. Sáfrán<sup>2</sup>, W. Seidel, M. Sisti<sup>3</sup>,  
L. Stodolsky, S. Uchaikin

*Max-Planck-Institut für Physik, Föhringer Ring 6, 80805 München, Germany*

Received 8 November 2000; accepted 22 January 2001

---

## Abstract

The use of quasiparticle diffusion in a superconducting film has the potential to allow an increase in the size of a cryogenic detector without proportional loss of energy resolution. The quasiparticle lifetime and the diffusion constant are critical parameters which have limited this development. Using W superconducting phase transition thermometers as the sensors and a W/Al bilayer as the diffusion film, we have measured quasiparticle diffusion over a distance of 2 mm and deduced a diffusion constant of  $D = 2.5 \times 10^{-4} \text{ m}^2/\text{s}$  and a quasiparticle lifetime of  $\tau = 9.0 \text{ ms}$ , which is, to our knowledge, by far the longest ever observed. With Ir/Au thermometers and an Ir/Au/Al diffusion film we found  $D = 4.6 \times 10^{-3} \text{ m}^2/\text{s}$  and  $\tau = 0.43 \text{ ms}$  with diffusion over 4 mm, the longest distance observed to date. © 2001 Elsevier Science B.V. All rights reserved.

*PACS:* 29.40.Wk; 74.76.D6; 85.25.Am

*Keywords:* Cryogenic detector; Quasiparticle diffusion; Superconducting films

---

## 1. Motivation

We have studied the diffusion of quasiparticles in various superconducting films as part of our program to develop cryogenic particle detectors

for the search for dark matter particles. The quasiparticles were created by X-ray absorption in film strips of up to 4 mm length. After propagating through the film via diffusion they were trapped and detected in two superconducting phase transition thermometers at the ends of the strip. Position and energy of the absorbed X-rays as well as diffusion constants and lifetimes of the quasiparticles were determined. The very long observed lifetimes up to 9 ms should allow the realization of large area phonon collector films on massive cryogenic particle detectors.

In the following, we first describe the operation of our detectors without collector films, and then present the motivation for developing the use of such films.

---

<sup>\*</sup>Corresponding author. Present address: CEA Saclay, DSM/DAPNIA/SPP, F-91191 Gif-sur-Yvette Cedex, France. Tel.: +33-16908-7083; fax: +33-16908-6428.

*E-mail address:* loidl@hep.saclay.cea.fr (M. Loidl).

<sup>1</sup>Present address: University of Oxford, Department of Physics, Keble Road, Oxford OX1 3RH, UK.

<sup>2</sup>Permanent address: Hungarian Academy of Sciences, Research Institute for Technical Physics and Materials Science, P.O. Box 49, 1525 Budapest, Hungary.

<sup>3</sup>Present address: INFN, Sezione di Milano, Via Celoria 16, 20133 Milano, Italy.

In the CRESST (Cryogenic Rare Event Search using Superconducting Thermometers) experiment [1,2] we are using cryogenic detectors [3,4] to search for hypothetical dark matter particles, the so-called Weakly Interacting Massive Particles (WIMPs). The particle interactions, nuclear recoils in the case of WIMPs, take place in a dielectric absorber crystal where they create non-thermal phonons. As sensors for these phonons we are using superconducting phase transition thermometers: a small superconducting metal film on the crystal surface is stabilized at a temperature in the range of the phase transition between the normal and the superconducting states. The non-thermal phonons which enter the thermometer transfer their energy to its free electrons, and the resulting temperature rise is measured via the increasing electrical resistance.

To reduce the involved heat capacities and thermal and electrical noises we are using superconductors with very low critical temperatures: tungsten ( $T_c \approx 15$  mK) [4] or bilayers of iridium and gold using the proximity effect to reduce the critical temperature (112 mK) of Ir by a normal conducting Au layer to values between  $\sim 25$  and 100 mK [5]. At these low temperatures the thermal coupling between electrons and phonons is very weak so that the thermometer (electronic heat capacity) and the absorber (lattice heat capacity) are nearly thermally decoupled [6]. Therefore, the non-thermal phonons heat predominantly the thermometer rather than the absorber. The temperature rise is dominated by the deposited energy and the heat capacity of the thermometer. Thus, the heat capacity of the absorber hardly affects the amplitude of the signals. This allows the use of large mass absorbers without losing much in sensitivity as compared to smaller detectors.

Before entering the thermometer, the non-thermal phonons are typically scattered many times at the absorber surface. Even on clean and well-polished surfaces there is a certain probability for the scattering to be inelastic which leads to a thermalization of the phonons. The described detector concept requires most of the non-thermal phonons to be collected in the thermometer without thermalizing in the absorber. Since the time constant of the phonon collection is inversely

proportional to the collecting area, this implies a relatively large thermometer. However, since the heat capacity of the thermometer governs the signal amplitude, it would be advantageous to minimize its size.

This contradiction can be overcome by combining a small thermometer with a large-area phonon collector film made of a superconductor with a much higher critical temperature. In this case, the high energy phonons are collected in the film by breaking Cooper-pairs into highly excited quasiparticles. The quasiparticles relax very quickly towards the gap edge, emitting high frequency phonons. As long as the energy of these phonons exceeds twice the energy gap of the superconductor they create new quasiparticles. Due to a residual excitation over the gap edge the quasiparticles have a non-zero group velocity and propagate diffusively through the film. Once they reach the thermometer, whose energy gap vanishes at the transition temperature, they release their energy to the free electrons of the thermometer, causing a temperature rise.

The diffusion constant and lifetime of quasiparticles are of crucial importance for this detector concept. Since these quantities are hard to predict, a series of experiments has been carried out to determine them for the materials considered for the phonon collectors.

## 2. Detector fabrication

The quasiparticle diffusion was investigated in strips of superconducting films which were e-beam evaporated onto sapphire substrates. In order to achieve films of very high purity and crystalline quality, each material is evaporated in a dedicated UHV system [4,7]. Special care has been taken to avoid any sources of magnetic impurities near the substrates. The geometries of the films were defined by means of photolithography.

According to the use of the films in these experiments, in the following they will be referred to as diffusion films. Each of them is provided with two thermometers at its ends, as shown in Fig. 1. Two types of film arrangements were studied:

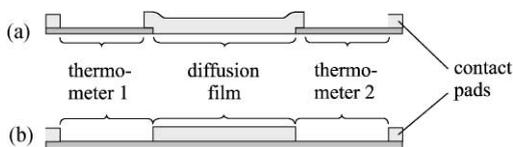


Fig. 1. Cross-section of the two types of film arrangements.

(a) an aluminum film of  $1\ \mu\text{m}$  thickness overlaps the edge of each thermometer by some  $10\ \mu\text{m}$  for an efficient transmission of the quasiparticles from the Al into the thermometer film, or

(b) the film of the thermometer material extends over the whole length of the film arrangement and a section in the middle is covered with an Al film of  $1\ \mu\text{m}$  thickness. The resulting bilayer serves as the diffusion film; due to the proximity effect it exhibits a critical temperature near  $1\ \text{K}$ . The uncovered areas at the ends of the bilayer remain as thermometers and are equipped with Al or Au contact pads.

In configuration (a) strong structural defects in the diffusion film are to be expected where it grows over the edges of the thermometers. This could cause a reduced efficiency of the quasiparticle trapping into the thermometers. In configuration (b) these edges are not present.

In either case, prior to the Al deposition a low energy Ar ion source is used to remove the oxide from the W surface to ensure a good metallic contact between the two layers. To be able to compare both film arrangements without any influence of the fabrication of the individual samples, on most of the detectors we prepared both film arrangements in the same sequence of processes.

### 3. Experimental procedure

The diffusion film and a small fraction of each thermometer were irradiated with an  $^{55}\text{Fe}$  source. An X-ray photon which is absorbed in the diffusion film creates a local population of quasiparticles which diffuse through the film to the thermometers, causing correlated temperature pulses in the two thermometers. X-rays which pass through the film are stopped in the substrate below and create non-thermal phonons which are col-

lected in the film and also excite quasiparticles in a small area.

The thermometers are read out with two DC-SQUIDS. Electrical contact is provided by superconducting Al bonding wires; the diffusion film is used as common ground contact for both thermometers. The thermal coupling is obtained by covering the back side of the substrate with gold and pressing it to the copper holder.

The SQUID output voltages were fed into a two-channel 12-bit transient digitizer and in parallel AC-coupled to a two-channel trigger unit. Correlated signals were recorded for subsequent data analysis including pulse shape analysis, by OR-coupling the two trigger channels and recording coincident time windows of both channels. Events showing pile-up or SQUID resets—which occur when the signal rise is too fast for the SQUID electronics to follow and lead to a loss of information on the pulse height—were removed.

After this a correction of the data for a thermal signal component was applied to obtain the pure quasiparticle signals: since the thermometers are thermally coupled only via the substrate, all the incoming energy is eventually released into the substrate. The resulting rise in temperature of the substrate is in turn measured by the thermometers, in addition to the quasiparticle signal. This effect is enhanced by the presence of additional film structures on the substrate which gather some part of the heat and release it slowly back to the substrate. This thermal contribution was subtracted from the signals.

## 4. Results and discussion

### 4.1. W/Al diffusion film

Fig. 2 shows a scatter-plot of the pulse heights of correlated signals obtained with a W/Al bilayer of  $2\ \text{mm}$  length as diffusion film (configuration (b)). Two pairs of bent lines are seen in this plot: The two lines at higher energies are due to absorption of Mn  $K_\alpha$  and  $K_\beta$  X-rays in the W/Al film, the lines at lower energies to absorption in the substrate. The curvature of the lines reflects quasiparticle losses which are quite small for a

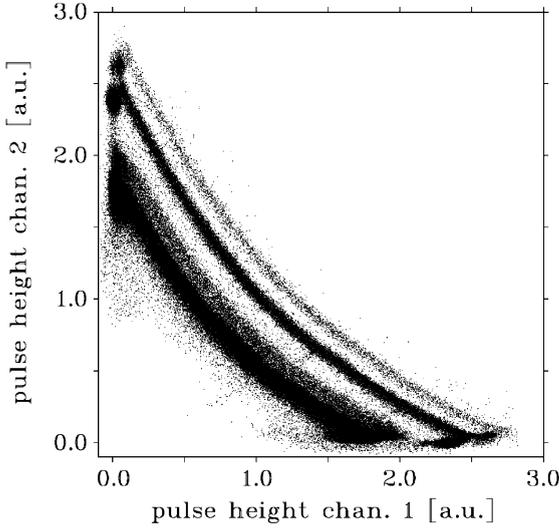


Fig. 2. Pulse heights of correlated signals from the two thermometers after subtraction of a thermal signal component.

distance of 2 mm, as compared to related experiments using superconducting tunnel junctions as quasiparticle sensors [8,9]. The intensity ratio of  $\sim 30/70$  between the two pairs of lines corresponds to the expected absorption in the W/Al bilayer.

Denoting the length of the diffusion film as  $L$  and the coordinate of the event position along the strip as  $x$  with the origin in the middle of the strip, the bent lines are described [10] by

$$N_{1,2}(x) = N_0 \frac{\sinh \alpha(\frac{1}{2} \mp \frac{x}{L}) + \beta \cosh \alpha(\frac{1}{2} \mp \frac{x}{L})}{(1 + \beta^2) \sinh \alpha + 2\beta \cosh \alpha}. \quad (1)$$

$N_0$  is the number of quasiparticles after relaxation to the gap edge;  $N_{1,2}(x)$  are the numbers of quasiparticles detected in thermometer 1 and thermometer 2, respectively;  $\alpha = L/\sqrt{D\tau}$  accounts for the loss of quasiparticles due to the recombination with a time constant  $\tau$ ;  $D$  is the diffusion constant;  $\beta = \sqrt{\tau_{tr}/\tau}$  reflects the imperfect quasiparticle trapping into the thermometers with a finite time constant  $\tau_{tr}$ .

A fit of Eq. (1) to the data yields the parameters  $\alpha$  and  $\beta$ . By solving Eq. (1) for  $N_0$  and  $x$  one can then calculate the energy and the position of each event from the measured pulse heights:

$$N_0 = \sqrt{(N_1\gamma_1 + N_2\gamma_2)(N_1\gamma_2 + N_2\gamma_1)}, \quad (2)$$

$$x = \frac{L}{2\alpha} \ln \left( \frac{N_1\gamma_1 + N_2\gamma_2}{N_1\gamma_2 + N_2\gamma_1} \right), \quad (3)$$

with  $\gamma_{1,2} = (1 \mp \beta)e^{\mp\alpha/2}$ .  $N_0$  is directly proportional to the deposited energy and can be calibrated by the detection of X-rays of a known energy.

The result is shown in Fig. 3, with the deposited energy plotted versus the event position. Within a section of 0.25 mm length in the middle of the strip, an energy resolution of 149 eV (FWHM) for 6 keV X-ray events in the W/Al film was obtained. This corresponds to a spatial resolution of  $\sim 50 \mu\text{m}$ . As can be seen from the width of the lines in Fig. 3, the energy resolution is roughly constant over the full length of the strip. The slight tilt of the lines of constant energy in this plot is due to a slightly different trapping efficiency of the two thermometers whereas in the calculation only one averaged value of  $\beta$  was used.

In Fig. 4 the time difference between the pulse onsets of correlated signals is plotted as a function of the calculated event position. This time difference has also been simulated on the basis of the diffusion equation and fit to the data, as shown by the solid line in Fig. 4. The fit gives the value of the diffusion constant  $D$  and, combined with the

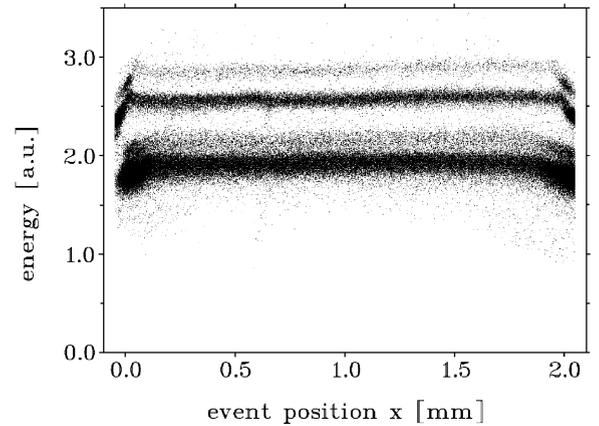


Fig. 3. Deposited energy versus event position  $x$  along the diffusion strip. The strong clusters of events at 0 and 2 mm correspond to thermometer hits. As in Fig. 2, the two lines at higher energies reflect absorption of Mn  $K_\alpha$  and  $K_\beta$  X-rays in the W/Al film, the lines at lower energies absorption in the substrate.

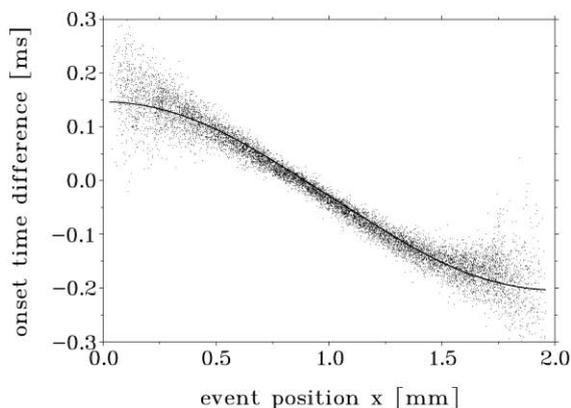


Fig. 4. Time difference between pulse onsets in the two channels versus event position; for this plot only film events have been selected. The solid line is a fit curve of the calculated onset time difference.

previously determined value of  $\alpha$ , the quasiparticle lifetime  $\tau$ .

In this W/Al bilayer a very low diffusion constant of  $D = 2.5 \times 10^{-4} \text{ m}^2/\text{s}$  was obtained. The diffusion can take place in both W and Al, and W has a very short mean free path. The quasiparticle lifetime of  $\tau = 9.0 \text{ ms}$  is to our knowledge by far the longest one ever observed.

#### 4.2. Ir/Au/Al diffusion film

A detector with Ir/Au thermometers ( $T_c \approx 50 \text{ mK}$ ) and an Ir/Au/Al trilayer of 4 mm length as diffusion film (configuration (b)) showed somewhat higher quasiparticle losses per unit length. This is due to a shorter lifetime of 0.43 ms partially counteracted by a higher diffusion constant of  $4.6 \times 10^{-3} \text{ m}^2/\text{s}$ . The energy resolution within a 0.25 mm section in the middle of the detector was 320 eV (FWHM). The performance of this device was not as good as that of the W/Al detector. However, the length of this film is to our knowledge the longest distance over which quasiparticle diffusion has been observed to date.

#### 4.3. Al diffusion film

Aluminum single layers as diffusion films (configuration (a)) gave much poorer results. The quasiparticle losses were much higher, and the

energy resolution was much worse. A quasiparticle lifetime of  $\tau \approx 0.1 \text{ ms}$  was determined. The reason for this unexpected result was found by a transmission electron microscope investigation of one of the detectors [11]: on the tungsten film aluminum grows as a single crystalline film whereas on the sapphire substrate it is polycrystalline with typical grain sizes around  $1 \mu\text{m}$ . This is due to the above mentioned ion bombardment prior to the Al deposition, which causes the sapphire surface to become amorphous (as observed with a RHEED system). In contrast, the surface of the tungsten film is sputtered off but the crystalline structure remains unaffected, allowing the epitaxial growth of the subsequently evaporated Al film.

### 5. Test detector with a W/Al phonon collector film

Based on the good results obtained with the detector of Section 4.1, a first massive test detector

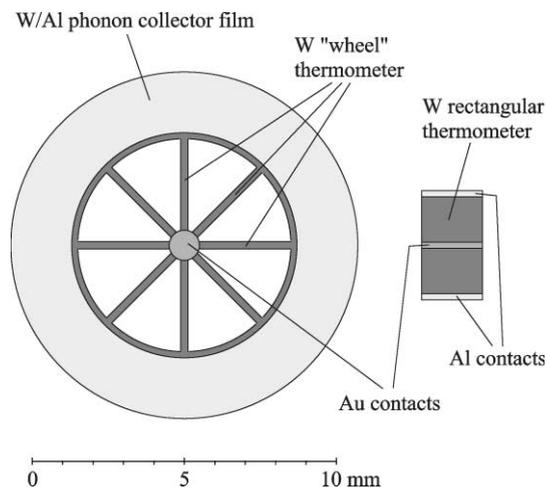


Fig. 5. The two film structures on the test detector. The thermometers are represented in dark grey. In the left structure the parallel connection of the spokes between the central Au contact and the rim of the wheel serves as thermometer. Its area ( $3 \times 2 \text{ mm}^2$ ) equals that of the rectangular thermometer. The wheel thermometer is surrounded by a W/Al phonon collector film which, as it is superconducting, provides also a homogeneous potential on the entire circumference of the wheel. The total area of the wheel structure including the phonon collector film is 10 times that of the rectangle.

was fabricated with a 32 g sapphire crystal and a large-area W/Al phonon collector film. In order to minimize the distance for the quasiparticles to travel for a given film area, a new geometry was designed (see Fig. 5). The W thermometer was patterned into the form of a wheel, with eight spokes of  $3 \times 0.25 \text{ mm}^2$  between a central gold contact and the rim of the wheel. The rim has a width of 2.2 mm. The outer 2 mm were covered with Al to form the collector film. The inner 0.2 mm were left as pure W to connect the spokes thermally in parallel and to allow quasiparticles to enter the W film along the entire circumference. The resistance was measured between the central contact and the rim, using the superconducting W/Al bilayer as the outer contact. The thermal coupling to the heat sink was given by a gold wire bonded onto the gold contact and onto the copper detector holder.

To be able to directly measure the efficiency of energy collection and transport in the collector film, a second, rectangular W thermometer without a collector film has been evaporated onto the same sapphire crystal. Its length and width ( $3 \times 2 \text{ mm}^2$ ) correspond to the parallel connection of the spokes of the wheel thermometer. Together with its Al and Au contacts it has an area of  $7.2 \text{ mm}^2$ ; the wheel including the collector film has a total area of  $72 \text{ mm}^2$ . The heat capacity of the superconducting W/Al bilayer is negligible, but due to the W rim the heat capacity of the wheel is a factor 1.6 higher than that of the rectangle. The collection of non-thermal phonons created by interactions in the sapphire crystal is shared between the two film structures, according to their respective areas.

Due to the very broad and non-linear phase transitions of the thermometers of this detector its energy resolution was poor. However, the total efficiency of phonon collection and quasiparticle transport turned out to be very high. Taking into account the areas and the heat capacities of the two film structures, a maximal ratio of 6 was expected for the amplitudes of the temperature signals, if there were no quasiparticle losses. However, the measurement gave a ratio of 18. An explanation for this is that not only the quasiparticle losses are very small but also the

phonon collection is more efficient in the W/Al bilayer than in the W thermometer. The free electrons of the thermometer interact mainly with longitudinal phonons [13]. In contrast, the excitation of quasiparticles in the collector film is equally efficient for transverse phonons, which dominate the phonon population.

In the CDMS dark matter search experiment a similar concept with a complex film structure is being used for phonon collection. Many small W thermometer elements are connected with Al collector fins on these detectors. It has been found that only about 6% of the quasiparticles arrive in the thermometers [12]. With our W/Al bilayers a much higher efficiency has been achieved. For a first attempt this result was very promising. After more detailed studies and optimization it may allow the development of detectors with even higher mass than the presently used CRESST detectors, maintaining their high energy resolution and low threshold.

## 6. Conclusions

Quasiparticle diffusion has been observed over distances up to 4 mm, which is promising for the use of diffusion films in cryogenic detectors needing large sensitive areas. A very long lifetime of 9 ms has been observed in a W/Al bilayer, but lower values of 0.4 and 0.1 ms in Ir/Au/Al and polycrystalline Al films, respectively, show that the lifetime depends strongly on the film parameters. In all cases the diffusion constants were 1–2 orders of magnitude smaller than expected for quasiparticles relaxed to a thermal distribution at the respective temperature. Such an unexpectedly slow quasiparticle diffusion seems to be a common experimental observation (e.g. [9,14]).

Diffusion films could be used in two types of cryogenic detectors. X-ray detectors for use in astronomy need both energy and position resolution. This could be provided by comparing the signals in four thermometers on the four sides of a quadratic diffusion film in which the X-rays are absorbed. Larger sensitive areas could be achieved than have been reached so far in similar developments using tunnel junctions (e.g. [15–17]) but the

slow diffusion in our films limits the achievable counting rate.

The second possible application is in large mass detectors, as used in the CRESST dark matter search, where the film could be used to increase the phonon collection area without increasing the heat capacity of the sensor. In this type of experiment the counting rate limit is not important and the diffusion film should allow the use of even larger absorber crystals. The feasibility of this concept has recently been demonstrated with a first test detector with a large area phonon collector film.

### Acknowledgements

The authors would like to thank J. Schnagl for providing the Ir/Au film. This work was supported by the SFB 375 Particle Astrophysics and the EC-network ERBFMRXCT980167.

### References

- [1] M. Bravin et al., *Astropart. Phys.* 12 (1999) 107.
- [2] M. Sisti et al., in: P. de Korte, T. Peacock (Eds.), *Proceedings of the Eighth International Workshop on Low Temperature Detectors (LTD-8)*, Dalfsen, Netherlands, 15–20 August 1999, *Nucl. Instr. and Meth. A* 444 (2000) 312.
- [3] M. Sisti et al., *Nucl. Instr. and Meth. A* (2000), accepted.
- [4] P. Colling et al., *Nucl. Instr. and Meth. A* 354 (1995) 408.
- [5] U. Nagel et al., *J. Appl. Phys.* 78 (1994) 4262.
- [6] F. Pröbst et al., *J. Low Temp. Phys.* 100 (1995) 69.
- [7] J. Höhne et al., *Nucl. Instr. and Meth. A* 370 (1996) 160.
- [8] P. Hettl et al., in: S. Cooper (Ed.), *Proceedings of the Seventh International Workshop on Low Temperature Detectors (LTD-7)*, Munich, Germany, 27 July–2 August 1997, p. 52, avail. from U. Grenzemann, MPI für Physik, Föhringer Ring 6, 80805 München, Germany.
- [9] K. Segall et al., in: S. Cooper (Ed.), *Proceedings of the Seventh International Workshop on Low Temperature Detectors (LTD-7)*, Munich, Germany, 27 July–2 August 1997, p. 47, avail. from U. Grenzemann, MPI für Physik, Föhringer Ring 6, 80805 München, Germany.
- [10] J. Jochum et al., *Ann. Physik* 2 (1993) 611.
- [11] G. Sáfrán et al., Cross-sectional TEM study of superconducting X-ray detectors based on thin W/Al layers, to be published.
- [12] T. Saab et al., in: P. de Korte, T. Peacock (Eds.), *Proceedings of the Eighth International Workshop on Low Temperature Detectors (LTD-8)*, Dalfsen, Netherlands, 15–20 August 1999, *Nucl. Instr. and Meth. A* 444 (2000) 300.
- [13] A.B. Pippard, *Philos. Mag.* 46 (1955) 1104.
- [14] M.L. van den Berg et al., in: S. Cooper (Ed.), *Proceedings of the Seventh International Workshop on Low Temperature Detectors (LTD-7)*, Munich, Germany, 27 July–2 August 1997, p. 52, avail. from U. Grenzemann, MPI für Physik, Föhringer Ring 6, 80805 München, Germany.
- [15] G. Angloher et al., in: P. de Korte, T. Peacock (Eds.), *Proceedings of the Eighth International Workshop on Low Temperature Detectors (LTD-8)*, Netherlands, 15–20 August 1999, p. 214, *Nucl. Instr. and Meth. A* 444 (2000).
- [16] L. Li et al., in: P. de Korte, T. Peacock (Eds.), *Proceedings of the Eighth International Workshop on Low Temperature Detectors (LTD-8)*, Netherlands, 15–20 August 1999, p. 228, *Nucl. Instr. and Meth. A* 444 (2000).
- [17] E.C. Kirk et al., in: P. de Korte, T. Peacock (Eds.), *Proceedings of the Eighth International Workshop on Low Temperature Detectors (LTD-8)*, Netherlands, 15–20 August 1999, *Nucl. Instr. and Meth. A* 444 (2000) 201.